

Low Energy Properties of the (n,n) Carbon Nanotubes

Yu. A. Krotov ^(a), D.-H. Lee ^(a), and Steven G. Louie ^(a,b)

^(a) *Department of Physics, University of California at Berkeley, Berkeley, CA 94720*

^(b) *Materials Sciences Division, Lawrence Berkeley National Laboratory, Berkeley, CA 94720*

(February 1, 2008)

According to band theory, an ideal undoped (n,n) carbon nanotube is metallic. We show that the electron-electron interaction causes it to become Mott insulating with a spin gap. More interestingly, upon doping it develops superconducting fluctuations.

71.10.Hf, 71.10.Pm, 78.66.Tr

Carbon nano-structures such as C_{60} [1] and nanotubes [2] have attracted considerable interest recently. The latter is a graphite sheet wrapped into a cylinder form. A pair of integers (n, m) specifies the wrapping. Starting from a graphite sheet with the primitive lattice vectors $\vec{a}, \vec{b}$ making an angle of 60 degrees, the (n, m) tube is a cylinder with axis running perpendicular to $n\vec{a} + m\vec{b}$, so that atoms separated by $n\vec{a} + m\vec{b}$ are wrapped onto each other.

Considerable efforts have gone into studying the band-structure of carbon nanotubes [3]. The purpose of this work is to address the effects of electron-electron interaction on the low energy properties of them. In one-electron tight-binding description where one retains a single π orbital per atom and keeps only the nearest neighbor hopping, all $n \neq m$ tubes are band-insulators with gaps generally scaling inversely with the radius [3]. For these tubes a sufficiently weak electron-electron interaction is not expected to change the low energy properties qualitatively. The same can not be said of the (n,n) tubes, which are band metals. To be precise, for the latter two out of $4n$ bands intersect the Fermi level to form two Dirac points (Fig.1). Due to the low dimensionality and the presence of gapless excitations, the effects of electron-electron interaction must be examined more carefully.

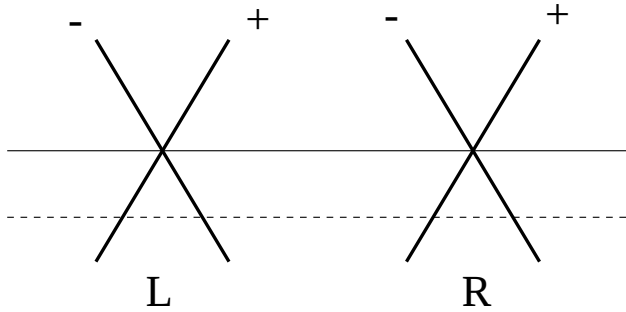


FIG. 1. The low-energy band structures of (n,n) tubes. “L” and “R” labels the Dirac points, “+”, “-” labels the right and left movers. The dashed line denotes the Fermi level in the doped case.

In this paper we perform perturbative renormaliza-

tion group (RG) calculations to analyze the asymptotic low energy behavior of the (n,n) tubes [4]. The microscopic Hamiltonian is consisted of a nearest-neighbor tight-binding model for the π orbital on each carbon atom (the bonding topology is illustrated in Fig. 2) and a Hubbard U plus a nearest neighbor V for electron correlations. To build up an effective model for low temperature, we first discard all bands that do not intersect the Fermi level. Second, we regard the two remaining bands as linearly dispersing, i.e., we ignore the energy dependence of the band velocity. Due to these approximations, a upper energy cutoff E_c has to be imposed on our subsequent discussions [5]. In the Hilbert space of the two bands, the original interactions U and V give rise to twelve independent scattering amplitudes g_{ijkl}^{abcd} .

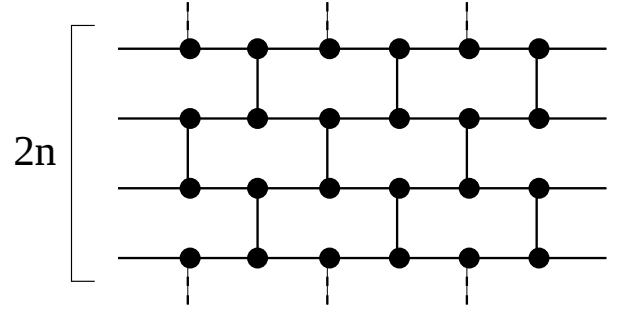


FIG. 2. The bonding structure of (n,n) tubes.

The effective Hamiltonian is given by $H = H_K + H_I$, where

$$H_K = \sum_{i=R,L} \sum_{a=\pm} \sum_{\sigma} (av_F) \int dx \psi_{ia\sigma}^\dagger(x) \frac{\partial_x}{i} \psi_{ia\sigma}(x)$$

$$H_I = \sum \frac{g_{ijkl}^{abcd}}{2} \int dx \psi_{ia\sigma}^\dagger(x) \psi_{jb\sigma'}^\dagger(x) \psi_{kc\sigma'}(x) \psi_{ld\sigma}(x). \quad (1)$$

In the second line of Eq.(1) the sum is taken over $i, j, k, l = R, L$, $a, b, c, d = \pm$, and $\sigma, \sigma' = \uparrow, \downarrow$. The operator $\psi_{i\pm\sigma}^\dagger(k) = \int dx e^{ikx} \psi_{i\pm\sigma}^\dagger(x)$ creates an right/left moving electron with momentum $k_i + k$ and with spin σ . Here k_i is the momenta associated with the right (R) or left (L) Dirac points (Fig.1). The only nonzero g 's in Eq.(1) are those whose lower and upper indices have the

form: $(RRRR)$, $(RLRL)$, $(RLLR)$, and $(++++)$, $(++--)$, $(+-+-)$, $(+--+)$, plus those generated by $+ \leftrightarrow -$ and/or $R \leftrightarrow L$. We abbreviate the twelve independent coupling constant as g_i^j , where $i = 1, 2, 4$; $j = 1, 2, 3, 4$ [6].

We then perform a one-loop RG calculation, which is a straightforward generalization of the one-band calculation [7]. The only complication is that instead of four, there are twelve independent scattering amplitudes. This calculation yields:

$$\begin{aligned}\frac{dg_1^1}{dx} &= -g_1^3g_1^3 + g_1^3g_2^3 - g_1^1g_1^1 - g_1^2g_2^1, \\ \frac{dg_1^2}{dx} &= g_4^2g_1^2 + g_4^3g_1^3 - g_1^2g_2^2 - g_2^1g_1^1, \\ \frac{dg_1^3}{dx} &= -2g_1^3g_1^1 + g_1^3g_2^2 + g_2^3g_1^1 + g_4^2g_1^3 + g_4^3g_1^2, \\ \frac{dg_2^1}{dx} &= g_4^2g_1^1 + g_4^1g_2^2 - 2g_4^1g_2^1 + g_4^3g_1^3 - g_4^3g_2^3 - g_2^1g_1^1 - g_2^1g_2^2, \\ \frac{dg_2^2}{dx} &= \frac{1}{2}(g_2^3g_2^3 - g_1^2g_1^2 - g_2^1g_2^1 - g_1^1g_1^1), \\ \frac{dg_2^3}{dx} &= g_2^3g_2^2 + g_4^2g_2^3 + g_4^1g_1^3 - 2g_4^1g_2^3 + g_4^3g_1^2 - g_4^3g_2^1, \\ \frac{dg_4^1}{dx} &= -g_4^1g_4^1 + g_1^3g_2^3 - g_2^3g_2^3 + g_2^1g_2^1 - g_2^1g_2^2, \\ \frac{dg_4^2}{dx} &= \frac{1}{2}(g_4^3g_4^3 - g_4^1g_4^1 + g_1^3g_1^3 + g_1^2g_1^2), \\ \frac{dg_4^3}{dx} &= -g_4^3g_4^1 + 2g_4^3g_4^2 - 2g_2^3g_2^1 + g_1^3g_2^1 + g_2^3g_1^2 + g_1^3g_1^2, \quad (2)\end{aligned}$$

plus $\frac{dg_4^4}{dx} = \frac{dg_2^4}{dx} = \frac{dg_4^4}{dx} = 0$. In the above $x \equiv \frac{1}{\pi v_F} \ln(\frac{E_c}{E})$, where E_c and E are initial and running energy cutoffs respectively.

To draw the implications from the RG equations we compute correlation functions $\chi_\alpha(\omega) = \int dx dt e^{i\omega t} < T[O_\alpha(x, t) O_\alpha^\dagger(0, 0)] >$ for the following O_α :

$$\begin{aligned}O_{CDW1}(x) &= \sum_\sigma \psi_{R+\sigma}^\dagger(x) \psi_{R-\sigma}(x), \\ O_{SDW1}(x) &= \frac{1}{2}[\psi_{R+\uparrow}^\dagger(x) \psi_{R-\uparrow}(x) - \psi_{R+\downarrow}^\dagger(x) \psi_{R-\downarrow}(x)] \\ O_{SS1}(x) &= \frac{1}{\sqrt{2}}[\psi_{R+\uparrow}^\dagger(x) \psi_{R-\downarrow}^\dagger(x) - \psi_{R+\downarrow}^\dagger(x) \psi_{R-\uparrow}^\dagger(x)], \\ O_{TS1}(x) &= \psi_{R+\uparrow}^\dagger(x) \psi_{R-\uparrow}^\dagger(x), \\ O_{CDW2}(x) &= \sum_\sigma \psi_{R+\sigma}^\dagger(x) \psi_{L-\sigma}(x), \\ O_{SDW2}(x) &= \frac{1}{2}[\psi_{R+\uparrow}^\dagger(x) \psi_{L-\uparrow}(x) - \psi_{R+\downarrow}^\dagger(x) \psi_{L-\downarrow}(x)], \\ O_{SS2}(x) &= \frac{1}{\sqrt{2}}[\psi_{R+\uparrow}^\dagger(x) \psi_{L-\downarrow}^\dagger(x) - \psi_{R+\downarrow}^\dagger(x) \psi_{L-\uparrow}^\dagger(x)], \\ O_{TS2}(x) &= \psi_{R+\uparrow}^\dagger(x) \psi_{L-\uparrow}^\dagger(x). \quad (3)\end{aligned}$$

plus those generated by $R \leftrightarrow L$ and/or $+ \leftrightarrow -$. In the above CDW, SDW, SS and TS stand for charge density wave, spin density wave, singlet superconductivity and triplet superconductivity respectively. These correlation

functions are chosen because of their logarithmic divergence in the absence of interaction. To the lowest order in g 's, the results are

$$\chi_\alpha = N_\alpha \chi_0(\omega) \left(\frac{E_c}{\omega}\right)^{K_\alpha}. \quad (4)$$

Here $\chi_0 = \frac{1}{2\pi v_F} \ln(\frac{E_c}{\omega})$, and all N_α are unity except that $N_{CDW1} = N_{CDW2} = 2$. Finally the exponents are $K_{CDW1} = \frac{g_4^2 - 2g_4^1}{2\pi v_F}$, $K_{SDW1} = \frac{g_4^2}{2\pi v_F}$, $K_{SS1} = -\frac{g_4^2 + g_4^1}{2\pi v_F}$, $K_{TS1} = \frac{g_4^1 - g_4^2}{2\pi v_F}$, $K_{CDW2} = \frac{g_2^2 - 2g_1^1}{2\pi v_F}$, $K_{SDW2} = \frac{g_2^2}{2\pi v_F}$, $K_{SS2} = -\frac{g_2^2 + g_1^1}{2\pi v_F}$, $K_{TS2} = \frac{g_1^1 - g_2^2}{2\pi v_F}$.

I. The undoped case. The bare values of the coupling constants are $g_2^1 = g_2^3 = g_4^1 = g_4^3 = U - V$, $g_1^1 = g_1^2 = g_1^3 = g_1^4 = U$, $g_2^2 = g_2^4 = g_4^2 = g_4^4 = U + V$. We solve Eq.(2) numerically for $V/U \leq 1$ and find that in all cases the absolute values of all coupling constants eventually diverge. As to the susceptibilities, we find that for $\frac{V}{U} < (\frac{V}{U})_c \approx 0.8$ the most divergent susceptibility is χ_{SDW1} , and for $(\frac{V}{U})_c < \frac{V}{U} < 1$ the most divergent susceptibility is χ_{CDW2} .

Ia) The SDW1 Phase: For $\frac{V}{U} < (\frac{V}{U})_c$ we perform a mean-field theory using the *renormalized* Hamiltonian. Guided by the susceptibility result, we introduce $M_R = < O_R(x) >$ and $M_L = < O_L(x) >$, where

$$\begin{aligned}O_R(x) &= \frac{1}{2}[\psi_{R+\uparrow}^\dagger(x) \psi_{R-\uparrow}(x) - \psi_{R+\downarrow}^\dagger(x) \psi_{R-\downarrow}(x)] \\ O_L(x) &= \frac{1}{2}[\psi_{L+\uparrow}^\dagger(x) \psi_{L-\uparrow}(x) - \psi_{L+\downarrow}^\dagger(x) \psi_{L-\downarrow}(x)] \quad (5)\end{aligned}$$

as the order parameters. The mean-field Hamiltonian is the factorized form

$$\begin{aligned}H &= H_K - g_4^3 \int dx [O_R O_R + O_R^\dagger O_R^\dagger + O_L O_L + O_L^\dagger O_L^\dagger] \\ &\quad - 2g_4^2 \int dx [O_R^\dagger O_R + O_L^\dagger O_L] - 2g_1^3 [O_L O_R + O_R^\dagger O_L^\dagger] \\ &\quad - 2g_1^2 \int dx [O_L^\dagger O_R + O_R^\dagger O_L]. \quad (6)\end{aligned}$$

In the range of V/U considered here the renormalized values of all the g 's appearing in Eq.(6) are positive. Consequently, the mean-field solution predicts $M_R = M_R^* = M_L = M_L^* = M_0$. It is important to note that the term proportional to g_4^3 demands both M_R and M_L to be real and the term proportional to g_1^2 requires them to have the same sign. Consequently, the mean-field theory completely fixes the U(1) phases of the order parameters M_R and M_L . The only global degree of freedom left is the SU(2) rotation of the order parameter away from the spin z-direction. The Goldstone mode associated with the latter governs the low energy physics of the SDW1 phase. Indeed, let us define

$$\begin{aligned}Q_{\sigma\sigma'}(x) &= < \psi_{R+\sigma}^\dagger(x) \psi_{R-\sigma'}(x) - \frac{\delta_{\sigma\sigma'}}{2} \psi_{R+\tau}^\dagger(x) \psi_{R-\tau}(x) > \\ &\quad + < \psi_{L+\sigma}^\dagger(x) \psi_{L-\sigma'}(x) - \frac{\delta_{\sigma\sigma'}}{2} \psi_{L+\tau}^\dagger(x) \psi_{L-\tau}(x) > + h.c. \quad (7)\end{aligned}$$

The repeated indices imply summation. The mean field solution corresponds to $Q_{\sigma\sigma'} = Q_{\sigma\sigma'}^0 = 2\sigma M_0 \delta_{\sigma\sigma'}$. A smooth twist in the direction of the order parameter corresponds to $Q_{\sigma\sigma'} = [U^\dagger Q^0 U]_{\sigma\sigma'}$, where U is a smooth space-time dependent $SU(2)$ matrix. After a proper rescaling of the space and time coordinates, the effective action governing the dynamics of such twists is

$$S_\sigma = \frac{g}{2} \int dt dx Tr[(\partial_\mu Q)^2]. \quad (8)$$

Unlike the half-filled one-band Hubbard model, the effective action does not contain a topological term. This is because there are two Dirac points instead of one. Indeed, it can be shown that each Dirac point contributes a topological term with coefficient π [8]. Thus when added together, their effects cancel! [9] The 1+1 dimensional non-linear σ model given by Eq.(8) is always disordered [10], which indicates a gap in the spin spectrum [11].

Ib) The CDW2 Phase: For $1 > \frac{V}{U} > (\frac{V}{U})_c$, the most divergent susceptibility is χ_{CDW2} . Therefore we introduce $\Delta_1 = \langle O_1(x) \rangle$ and $\Delta_2 = \langle O_2(x) \rangle$ where

$$\begin{aligned} O_1(x) &= \sum_\sigma \psi_{R+\sigma}^\dagger(x) \psi_{L-\sigma}(x) \\ O_2(x) &= \sum_\sigma \psi_{L+\sigma}^\dagger(x) \psi_{R-\sigma}(x), \end{aligned} \quad (9)$$

as order parameters. The mean-field Hamiltonian is the factorized form of

$$\begin{aligned} H &= H_K + \frac{1}{2}(2g_1^3 - g_2^3) \int dx [O_1 O_2 + O_1^\dagger O_2^\dagger] \\ &+ \frac{1}{2}(2g_1^1 - g_2^2) [O_1^\dagger O_1 + O_2^\dagger O_2]. \end{aligned} \quad (10)$$

For the range of V/U considered here the renormalized $(2g_1^3 - g_2^3)$ and $(2g_1^1 - g_2^2)$ are positive and negative respectively. In the mean-field theory the term proportional to $(2g_1^3 - g_2^3)$ sets the sum of the phases of Δ_1 and Δ_2 to π , i.e., $\Delta_1 = -\Delta_2^*$. The mean-field solution is not unique, there being a family of equivalent mean-field solutions related by the $\Delta_1 \rightarrow e^{i\theta} \Delta_1$ and $\Delta_2 \rightarrow e^{-i\theta} \Delta_1$ transformation. This continuous degeneracy reflects the symmetry of Eq.(10) under this transformation. Under such circumstance there will be a Goldstone mode. To determine the effective action for the latter, we let $\Delta_1(x, t) = \Delta_0 e^{i\theta(x, t)}$ and $\Delta_2(x, t) = -\Delta_0 e^{-i\theta(x, t)}$ in the mean-field Hamiltonian and integrate out the electronic degrees of freedom [8]. (In the above $\theta(x, t)$ is a smooth space-time function). To determine whether or not this mode is charged, we impose a background electric field E . The details of such calculation will be reported elsewhere [9], but the following is the answer. After proper rescaling of x and t the effective action for ϕ is

$$S_g = \frac{K}{2} \int dt dx (\phi^* \frac{\partial_\mu}{i} \phi)^2, \quad (11)$$

where $\phi \equiv e^{i\theta}$. The lack of electric field dependence in Eq.(11) indicates that the Goldstone mode is neutral.

II. The doped case. In the doped case $g_4^3 = g_1^3 = g_2^3 = 0$. Integrating Eq.(2) numerically for $V/U < 1$, we see that the absolute values of all coupling constants again eventually diverge. In this case there are three phases. For $\frac{V}{U} < (\frac{V}{U})_{c1} \approx 0.55$ the most divergent susceptibility is the superconducting χ_{SS2} ! For $(\frac{V}{U})_{c1} < \frac{V}{U} < (\frac{V}{U})_{c2} \approx 0.65$ the most divergent susceptibility is χ_{SDW1} . Finally for $(\frac{V}{U})_{c2} < \frac{V}{U} < 1$ the most divergent susceptibility is χ_{CDW1} .

IIa) The SS2 phase For $\frac{V}{U} < (\frac{V}{U})_{c1}$ we introduce $\Delta_1 = \langle b_1(x) \rangle$ and $\Delta_2 = \langle b_2(x) \rangle$ as the order parameters where

$$\begin{aligned} b_1^+(x) &= \frac{1}{\sqrt{2}} [\psi_{R+\uparrow}^\dagger(x) \psi_{L-\downarrow}^\dagger(x) - \psi_{R+\downarrow}^\dagger(x) \psi_{L-\uparrow}^\dagger(x)] \\ b_2^+(x) &= \frac{1}{\sqrt{2}} [\psi_{R-\uparrow}^\dagger(x) \psi_{L+\downarrow}^\dagger(x) - \psi_{R-\downarrow}^\dagger(x) \psi_{L+\uparrow}^\dagger(x)]. \end{aligned} \quad (12)$$

The mean-field Hamiltonian is the factorized form of [12],

$$\begin{aligned} H &= H_K + (g_1^1 + g_2^2) \int dx [b_1^+(x) b_1(x) + b_2^+(x) b_2(x)] \\ &+ (g_1^2 + g_2^1) \int dx [b_1^+(x) b_2(x) + b_2^+(x) b_1(x)]. \end{aligned} \quad (13)$$

For the range of V/U considered here, after sufficient steps of renormalization $g_1^1 + g_2^2$ becomes negative. Meanwhile, $g_1^2 + g_2^1$ stays positive. In the mean-field theory the term proportional to $(g_1^2 + g_2^1)$ sets $\Delta_1 = -\Delta_2$. There is also a continuous family of mean-field solutions generated by the $\Delta_{1,2} \rightarrow e^{i\phi} \Delta_{1,2}$ transformation. This degeneracy reflects the global $U(1)$ invariance of Eq.(13). The Goldstone mode associated with ϕ dominates the low energy physics of the SS2 phase. If we let $\Delta(x, t) = \Delta_0 e^{i\theta(x, t)}$, after proper rescaling of x and t the effective action for the Goldstone mode is

$$S'_g = \frac{K}{2} \int dt dx [\phi^* (\frac{\partial_\mu}{i} - 2A_\mu) \phi]^2. \quad (14)$$

Here $\phi \equiv e^{i\theta}$ and A_μ is the external gauge field. The factor of two in front of A_μ reflects the fact that the Cooper pair is doubly charged.

Now we address the effect of impurities on superconductivity. Nanotubes often have impurities. For a single impurity the following terms are added to the Hamiltonian:

$$H_{imp} = \sum_{i,j=R,L} \sum_{a,b=\pm} u_{ij}^{ab} [\psi_{ia\sigma}^+(0) \psi_{jb\sigma}(0) + h.c.]. \quad (15)$$

In the above “0” is the position of the impurity. The one-loop RG equations for u_{ij}^{ab} are:

$$\begin{aligned} \frac{du_{LR}^{-+}}{dx} &= \frac{1}{2} (g_2^2 - 2g_1^1) u_{LR}^{-+} \\ \frac{du_{RR}^{-+}}{dx} &= \frac{1}{2} (g_4^2 + g_1^2 - 2g_4^1 - 2g_2^1) u_{RR}^{-+}, \end{aligned} \quad (16)$$

plus six other equations obtained by $R \leftrightarrow L$ and $+ \leftrightarrow -$. All other u 's do not renormalize. For positive bare u_{LR}^{-+}

and u_{RR}^{++} , u_{LR}^{++} eventually grows upon renormalization, while u_{RR}^{--} eventually shrinks. Nominally, we would drop the latter and keep only the former. However, within the range of coupling constants where we can trust our perturbative analyses, u_{LR}^{++} (u_{RR}^{--}) is only amplified (suppressed) by roughly a factor of two. For this reason, in the following we shall analyze the effects of all impurity scattering amplitudes on Cooper pairs.

We let an initial Cooper pair state $B^+(0)|0\rangle \equiv \frac{1}{\sqrt{2}}(b_1^+(0) - b_2^+(0))|0\rangle$ be scattered by various impurity scattering channels. The following are the results. 1) The terms introduced by $u_{LR}^{++}, u_{LR}^{--}, u_{RL}^{++}, u_{RL}^{--}$ annihilate the pair. 2) The terms introduced by $u_{RR}^{++}, u_{RR}^{--}, u_{LL}^{++}, u_{LL}^{--}, u_{LR}^{+-}, u_{LR}^{-+}, u_{RL}^{+-}, u_{RL}^{-+}$ break the pair. 3) The terms introduced by $u_{RR}^{+-}, u_{RR}^{-+}, u_{LL}^{+-}, u_{LL}^{-+}$ scatter it. Therefore a large amount of impurities can destroy superconductivity through 2), and produce Cooper pair localization through 3).

Iib) The SDW1 phase For $(\frac{V}{U})_{c1} < \frac{V}{U} < (\frac{V}{U})_{c2}$ our order parameters are the same as those defined in Eq.(5). The mean-field Hamiltonian is the factorized form of Eq.(6) except that g_1^3 and g_4^3 are set to zero. For the range of V/U considered here the renormalized values of g_4^2 and g_1^2 are both positive. Consequently, the term proportional to g_1^2 requires $M_R = M_L$. In this case, in addition to the global SU(2) freedom associated with the spin rotation, there remains a global U(1) freedom, i.e., $M_{R,L} \rightarrow e^{i\phi} M_{R,L}$. The effective action for the spin Goldstone mode is the same as that in Eq.(8), hence the spin excitations remain gapped. The effective action for the charge Goldstone mode is that of Eq.(11) excepts that an additional term arising from the chiral anomaly should be added.

$$S_g'' = S_g + S_{chiral}; \quad S_{chiral} = i\frac{4}{\pi} \int dx dt E \theta(x, t) \quad (17)$$

The last term reflects the fact that the U(1) Goldstone mode is a charged mode. The physical meaning of this mode is the sliding degree of freedom of the spin density wave.

Iic) The CDW1 phase For $(\frac{V}{U})_{c2} < \frac{V}{U} < 1$ we introduce $\Delta_R = \langle O_R(x) \rangle$ and $\Delta_L = \langle O_L(x) \rangle$ as order parameters. In the above

$$\begin{aligned} O_R(x) &= \sum_{\sigma} \psi_{R+\sigma}^{\dagger}(x) \psi_{R-\sigma}(x) \\ O_L(x) &= \sum_{\sigma} \psi_{L+\sigma}^{\dagger}(x) \psi_{L-\sigma}(x). \end{aligned} \quad (18)$$

The mean-field Hamiltonian is the factorized form of

$$H = H_K + \frac{1}{2}(2g_2^1 - g_1^2) \int dx [O_R O_L^{\dagger} + O_L O_R^{\dagger}]. \quad (19)$$

In the range of V/U considered here $2g_2^1 - g_1^2 < 0$. Consequently, mean-field theory gives $\Delta_R = \Delta_L$ with a global U(1) freedom, namely $\Delta_{R,L} \rightarrow e^{i\theta} \Delta_{R,L}$. The Goldstone mode associated with this U(1) freedom is again governed

by an action of the form Eq.(17). In this case ϕ describes the sliding mode of the charge density wave.

In this paper we use an on-site and nearest-neighbor interaction to model the screened Coulomb interaction. The effects of an unscreened Coulomb potential remain to be studied. In addition, we have not yet studied the nature of various phase transitions as a function of V/U . Finally, our recursion relation (Eq.(2)) has been obtained previously in studying various version of two-band models [13]. The relation between our model and the latter can be established via the identification that $(R, +) \leftrightarrow (A, R), (R, -) \leftrightarrow (B, L), (L, +) \leftrightarrow (B, R), (L, -) \leftrightarrow (A, L)$, where A and B labels the two bands.

Acknowledgement: We thank Professors Steven Kivelson, Paul McEuen and Doctor Vincent Crespi for helpful discussions. SGL acknowledges support of NSF Grant No. DMR 95-20554 and US DOE contract No. DE-AC03-76SF00098.

-
- [1] See e.g. "The Chemical Physics of Fullerenes - 10(5) years later", edited by W. Andreoni, Klusver Academic Publisher, 1996.
 - [2] S. Iijima, Nature (London) **354**, 56 (1991).
 - [3] N. Hamada, S. Sawada and A. Oshiyama, Phys. Rev. Lett. **68**, 1579 (1992); R. Saito, M. Fujita, G. Dresselhaus, and M.S. Dresselhaus, Appl. Phys. Lett. **60**, 2204 (1992); J.W. Mintmire, B.I. Dunlap and C.T. White, Phys. Rev. Lett. **68**, 631 (1992); X. Blase, L.X. Benedict, E.L. Shirley and S.G. Louie, Phys. Rev. Lett. **72**, 1878 (1994).
 - [4] Experimentally the fabrication of the (10,10) and other (n,n) tubes has been achieved. See e.g. A.Thess, Science **273**, 397 (1996).
 - [5] A word of caution is in order here. As n gets large, E_c continuously decrease. Indeed, the energy range in which our description remains valid shrinks to zero as $n \rightarrow \infty$!
 - [6] Here we have used the common convention, i.e., 1= inter-branch back scattering, 2=inter-branch forward scattering, 3=umklapp scattering, and 4=intra-branch forward scattering, to describe the structure among the upper and lower indices.
 - [7] J. Solyom, Adv. Phys. **28**, 201 (1979); R.Shankar, Rev.Mod.Phys. **66**, 129 (1994).
 - [8] M. Oshikawa and N. Nagaosa, J. Phys. Soc. Jpn., **65**, 2241 (1996).
 - [9] Yu.A. Krotov and D.-H. Lee to be published.
 - [10] A. M. Polyakov, Phys. Lett. B **59**, 79 (1975).
 - [11] F. D. M. Haldane, Phys. Lett. **93A**, 464 (1983); Phys. Rev. Lett. **50**, 1153 (1983); J. Appl. Phys. **57**, 3359 (1985).
 - [12] H. Suhl, B.T. Matthias and L.R. Walker, Phys. Rev. Lett. **12**, 552 (1959).
 - [13] C.M. Varma and A. Zawadowski, Phys. Rev. B **32**, 7399 (1985); A.M. Finkelstein and A.I. Larkin, Phys. Rev. B **47**, 10461 (1993); D.V. Khveshchenko and T.M. Rice,

Phys. Rev. B **50**, 252 (1994); H.J.Shulz, Phys. Rev. B **53**, R2959, (1996), L. Balents abd M.P.A. Fisher, Phys. Rev. B **53**, 12133, (1996); V.J. Emery, S.A. Kivelson and O. Zachar, cond-mat/9610094.